



Buckling analysis of three-dimensional functionally graded Euler-Bernoulli nanobeams based on the nonlocal strain gradient theory

Ahmad Soleimani ¹, Farshad Zamani ², Hamid Haghshenas Gorgani ^{3,*}

¹*Department of Mechanical Engineering, University of Jiroft, Jiroft, Iran*

²*Department of Mechanical Engineering, Isfahan University of Technology, Isfahan 84156-83111, Iran*

³*Engineering Graphics Center, Sharif University of Technology, Tehran, Iran*

Abstract

This paper presents a nonlocal strain gradient theory for capturing size effects in buckling analysis of Euler-Bernoulli nanobeams made of three-dimensional functionally graded materials. The material properties vary according to any function. These models can degenerate to the classical models if the material length-scale parameters is assumed to be zero. The Hamilton's principle applied to drive the governing equation and boundary conditions. Generalized differential quadrature method used to solve the governing equation. The effects of some parameters, such as small-scale parameters and constant material parameters are studied.

Keywords: Buckling analysis, Strain gradient elasticity theory, Nano beam, Three-directional functionally graded materials (TDFGMs), Generalized differential quadrature method (GDQM).

1. Introduction

Micro- and nanotechnology have recently found a special place in various sciences such as medicine and engineering. So the attention of scientists has focused on this science. With that in mind, mechanical engineers have done a lot of research to unravel the ambiguities of nanotechnology [1, 2]. One of the first problems was that classical mechanics did not have the ability to examine issues in the nano-scale. In order to solve this problem, reinforcement continuum mechanics theories have been proposed, which consider inherent characteristics of materials at the nano-scale [3, 4]. In recent decades, with the development of various engineering fields related to micro- and nano-systems, much attention has been given to size effects on material behaviors. Some advanced methods to address the weaknesses of the conventional theory are; Cosserat continuum mechanics [5], nonlocal elasticity [6-8], strain gradient elasticity [9], couple stress theory [10] and nonlocal strain gradient theory [11].

* Corresponding author, Professor, E-mail: h_haghshenas@sharif.edu

Among the non-classical continuum mechanics theories, nonlocal elasticity and strain gradient theory have been widely used to analyze the nanostructures [12-41]. According to the nonlocal elasticity theory, in contrast to classical elasticity, the stress tensor at an arbitrary point x in the domain of material depends not only on the strain tensor at x but also on strain tensor at all other points in the domain. According to this theory, a stress-strain relationship for a homogeneous elastic solid is:

$$\sigma_{ij}^{nl} = \int_v \alpha(|x' - x, \tau|) \sigma_{ij}^l dv(x')$$

where α is the nonlocal modulus or kernel function. It contains the small-scale effects incorporating into constitutive equations the nonlocal effects at the reference point x produced by local strain at the source x' . This function depends on two variables $|x - x'|$ and α . $|x - x'|$ represents the distance in Euclidean form and $\tau = e_0 \bar{a} / L$ is a material constant that depends on internal and external characteristic length (such as the lattice spacing and wavelength). The parameter e_0 is vital for the validity of nonlocal models. This parameter was determined by matching the dispersion curves based on atomistic models. Also, σ^{nl} is the nonlocal stress tensor at the reference point and σ^l is the classical stress tensor at local point. In addition, the classical stress tensor is defined as follows:

$$\sigma^l = C : \varepsilon$$

here C is the fourth order elasticity tensor and ‘:’ denotes the double dot product. Eringen determined the functional form of the kernel numerically. By appropriate choice of the kernel function, Eringen showed that the nonlocal constitutive equation given in integral form can be represented, for unbounded domains, in an equivalent differential form as:

$$(1 - \mu \nabla^2) \sigma^{nl} = C : \varepsilon, \quad \mu = (e_0 a)^2$$

On the contrary, for bounded structural domains, Eq.(1) is equivalent to a differential problem with suitable boundary constitutive conditions which are in contrast with equilibrium [42]. Accordingly, the elastostatic problem of a continuous nano-structure, formulated with Eringen’s integral model, admits no solution and hence such a theory cannot be adopted in nano-mechanics [43, 44]. The differential form of Eringen’s integral law is not adequate to analyze size effects in nano-beams [45]. A mathematically and mechanically well-posed model to investigate devices at nanoscale was proposed in [46] by a stress-driven integral methodology. Such an approach was successfully applied in [47] to study size-dependent dynamical behavior of a Bernoulli-Euler nano-beam. The stress-driven integral law exhibits, like strain gradient models, a hardening structural response for increasing values of the

nonlocal parameter. Recently, Lim et al. [48] pointed out the nonlocal strain gradient theory can predict both increase and decrease in the structural stiffness, a result confirmed by the experimental data [48]. These methods are widely used in modeling of nano structure problems. For example, Li and Hu [49] studied buckling behavior of a nonlinear Euler-Bernoulli simply supported beam of nonlocal strain gradient theory. Hamilton's principle was used to drive the governing equation and associated boundary conditions. Results show that post-buckling deflection has a positive relation to nonlocal parameter and reverse relation to material characteristic parameter. Besides, size dependent parameters have a significant effect on the higher-order buckling deflection. Li et al. [50] offered a model to investigate flexural wave propagation in the functionally graded beams based on nonlocal strain gradient theory. The effect of some parameters such as nonlocal parameter and material characteristic parameter were investigated. Farajpour et al. [51] used a higher-order nonlocal strain gradient in order to study thermoelastic buckling behavior of orthotropic size-dependent plate which is resting on the elastic foundation. Differential quadrature method was employed to solve the higher-order governing differential equation. They studied the effect of scale parameter, temperature and aspects of the plate on the buckling behavior of nanoplate. Ebrahimi and Barati [52] analyzed vibration through the thickness functionally graded smart nanobeams by using of a new nonlocal higher-order refined magneto-electro-viscoelastic model. They considered various boundary conditions for nanobeams. The effects of some parameters such as boundary conditions, damping coefficient, magnetic field and electric voltage on the natural frequency of nanobeams were studied. Nejad et al. [16-18] studied the bending, buckling and vibration behavior of nano-beams in the framework of nonlocal elasticity theory. They used Euler-Bernoulli beam model to analyze the nano-beams and considered that the mechanical property in nano-beam changed in the thickness and length directions according to arbitrary function. In these studies, the effects of length scale parameter and inhomogeneity parameter were explored. Tuns and Kirca [53, 54] presented an exact solution for integral form of Eringen's nonlocal theory in order to analyze bending and buckling of Euler-Bernoulli and Timoshenko nanobeams. Ebrahimi and Barati [55] studied wave propagation in the functionally graded nanobeams using of nonlocal strain gradient theory. Nanobeams were resting on an elastic foundation and was subjected to axial magnetic field. Results show that length scale parameter, material inhomogeneity parameter, elastic foundation and magnetic field have significant effect on the wave propagation behavior. Li et al. [56] investigated free vibration behavior of functionally graded size-dependent Timoshenko beams on the basis of nonlocal strain gradient theory. They used Hamilton's principle to drive governing equation and boundary conditions. Li and Hu [57] used nonlinear

Euler-Bernoulli and Timoshenko beam models along nonlocal strain gradient theory in order to study bending behavior of through the thickness functionally graded size-dependent beams. They show that the effect of small-scale parameter and material inhomogeneity parameter on the bending deflection and vibration frequency of size-dependent beams. Romanoff et al. [58] employed nonlocal sandwich Timoshenko beam theory in order to explain the macro- and micro-structural responses. Ebrahimi and Barati [59] investigate the influences of surface and thermal effects on the vibration analysis of viscoelastic Euler-Bernoulli nanobeams by using of nonlocal strain gradient theory. The nanobeams made of functionally graded material and resting on the viscoelastic foundation. Hamilton's principle was used to drive the governing equation and boundary conditions. They described the effects of damping coefficient on the vibration frequency of viscoelastic nanobeams. Based on the nonlocal strain gradient theory, Ebrahimi and Barati [60] offered a model for buckling behavior of higher order shear deformable curved nanobeams. Nanobeams were made of functionally graded material and mechanical properties varied according to power-law model. They investigate the effect of boundary conditions, material inhomogeneity parameter and length parameter. Xu et al. [61] investigated bending and buckling behavior of Euler-Bernoulli beams using of nonlocal strain gradient theory. Based on the nonlocal strain gradient theory, Li et al. [62] investigated bending, buckling and vibration behaviors through the length functionally graded Euler-Bernoulli size-dependent beams. They used Hamilton's principle to obtain the governing equation and associate boundary conditions. Then, generalized differential quadrature method was employed to solve these equations. Finally, they studied the effect of grading index and size-dependent parameter on the mechanical behaviors of beams. Li and Hu [63] derived torsional motion equation of nanotubes in the framework of nonlocal elasticity theory. Nanotubes made of functionally graded materials which the mechanical property was varying in the radius and length directions. Results show that torsional frequencies have reverse relation to nonlocal parameter.

Torsional vibration of nano-cone based on nonlocal strain gradient elasticity theory presented by Adeli et al. [20].

Functionally Graded Material (FGM) is one of the newest concepts in composite design. The properties of the FGM vary continuously from one point to another. Several articles dealing with different aspects of FGM have been published in recent years [12, 19, 22, 64-83]. It need to be cited that maximum of the above-noted analyses are associated with FGMs with material properties varying in a single direction only. However, there are practical occasions which require tailored grading of properties in two or even three directions. As reported by Steinberg [84],

Two-direction materials are needed in spacecraft design. Therefore, it is of great significance to develop novel FGMs with properties varying in two or three directions (2D or 3D FGMs) to withstand a more general temperature field.

In this article, using nonlocal strain gradient theory, buckling analysis of TDFGMs Euler-Bernoulli nano-beams is presented. The effects of changes of some important parameters are investigated.

2. Analysis

Consider a nano-beam of length L , width b , and thickness h made of three-directional functionally graded materials. Cartesian coordinates (x, y, z) are considered. The modulus of elasticity E are assumed to vary as arbitrary functions in axial, thickness and width directions, as indicated below [85]:

$$E(x, y, z) = X(x)Y(y)Z(z) \quad (1)$$

where $X(x)$, $Y(y)$ and $Z(z)$ are arbitrary functions.

Nonlocal elasticity theory, in contrast to classical elasticity, the stress tensor at an arbitrary point x in the domain of the material depends not only on the strain tensor at x but also on strain tensor at all other points in the domain. According to this theory, the structural stiffness of nanomaterials is smaller than that of the corresponding bulk material. Strain gradient theory in addition to the strain tensor, strain gradients are also considered in writing the strain energy density. Unlike to nonlocal elasticity theory, this theory predicts that the structural stiffness of nanomaterials is larger than that of the corresponding bulk material. Recently, by considering this problem, Lim et al. [11] demonstrate the nonlocal strain gradient theory that can predict both increase and decrease in the structural stiffness [85, 86].

In the nonlocal strain gradient theory, the total stress of Euler-Bernoulli beam are defined as

$$\sigma'_{xx} = \sigma_{xx} - \frac{d\sigma_{xx}^{(1)}}{dx} \quad (2)$$

here σ_{xx} and $\sigma_{xx}^{(1)}$ are the classical and higher-order nonlocal stress tensors, respectively. The constitutive equation of the nonlocal strain gradient theory can be expressed as;

$$\left[1 - \mu^2 \nabla^2\right] \sigma'_{xx} = E(1 - l^2 \nabla^2) \varepsilon_{xx} \quad (3)$$

where μ and l is the nonlocal and strain gradient material length scale parameter introduced to consider the significance of nonlocal strain gradient stress field.

Components of displacement vector (u_1, u_2, u_3) for Nano-beams based on Euler-Bernoulli beam theories can be expressed as

$$\begin{cases} u_1 = -z(\partial w/\partial x) \\ u_2 = 0 \\ u_3 = w(x,t) \end{cases} \quad (4)$$

Assuming the small deformations, the only nonzero strain of the Euler-Bernoulli beam theory is

$$\varepsilon_{xx} = \frac{\partial u}{\partial x} = -z \frac{\partial^2 w}{\partial x^2} \quad (5)$$

The governing equations of the FGM Euler-Bernoulli beam can be obtained, using the concept of minimum total potential energy principle. According to the principle of minimum total potential energy, the first variation in total potential energy must be zero.

$$\delta \Pi = \delta U + \delta V = 0 \quad (6)$$

in which δU and δV represent the variation of strain energy and that of virtual potential energy of axial load P , respectively. According to the nonlocal strain gradient theory developed by Lim et al. [48], variation of the strain energy density of an isotropic linear elastic material with volume Ω experiencing an infinitesimal displacement is defined as

$$\begin{aligned} \delta U &= \int_{\Omega} (\sigma_{xx} \delta \varepsilon_{xx} + \sigma_{xx}^{(1)} \nabla \delta \varepsilon_{xx}) dV = - \int_0^L M_{xx} \frac{\partial^2 \delta w}{\partial x^2} dx - M_{xx}^{(1)} \delta \frac{\partial^2 w}{\partial x^2} \Big|_0^L \\ &= -M_{xx}^{(1)} \delta \frac{\partial^2 w}{\partial x^2} \Big|_0^L - M \delta \frac{\partial w}{\partial x} \Big|_0^L + \frac{\partial M}{\partial x} \delta w \Big|_0^L - \int_0^L \frac{\partial^2 M_{xx}}{\partial x^2} \delta w dx \end{aligned} \quad (7)$$

where $\nabla \delta \varepsilon_{xx}$ is first-order strain gradient. M_{xx} and $M_{xx}^{(1)}$ is defined as follows:

$$M_{xx} = \int_A z \sigma'_{xx} dA \quad (8)$$

$$M_{xx}^{(1)} = \int_A z \sigma_{xx}^{(1)} dA \quad (9)$$

The first variation of the work due to the axial compressive force is given by:

$$\delta V = - \int_0^L P \frac{dw}{dx} \frac{d\delta w}{dx} dx = \int_0^L P \frac{d^2 w}{dx^2} \delta w dx \quad (10)$$

By substituting Eqs. (7) and (10) into Eq. (6) and using integration by parts, the motion equation is expressed as

$$\frac{\partial^2 M}{\partial x^2} = P \frac{d^2 w}{dx^2} \quad (11)$$

The classical boundary conditions is as follows

$$\begin{cases} w=0 & \text{or} & \frac{dM}{dx} = 0 \\ M=0 & \text{or} & \frac{dw}{dx} = 0 \end{cases} \quad (12)$$

and the non-classical boundary conditions

$$\frac{d^2 w}{dx^2} = 0 \quad \text{or} \quad M^{(1)} = 0 \quad (13)$$

By combining constitutive equation of the nonlocal strain gradient theory (3) and the equilibrium equation (11), we obtain the size-dependent Navier equation of TDFG beams on the basis of the nonlocal strain gradient theory and the Euler–Bernoulli beam theory

$$\begin{aligned} P \frac{d^2 w}{dx^2} - \mu^2 P \frac{d^4 w}{dx^4} = & -\frac{d^2 X}{dx^2} I_2 \frac{d^2 w}{dx^2} - 2 \frac{dX}{dx} I_2 \frac{\partial^3 w}{\partial x^3} + \left(l^2 \frac{d^2 X}{dx^2} - X \right) I_2 \frac{d^4 w}{dx^4} \\ & + 2l^2 I_2 \frac{dX}{dx} \frac{d^5 w}{dx^5} + l^2 I_2 X \frac{d^6 w}{dx^6} \end{aligned} \quad (14)$$

For convenience, the following nondimensionalizations are used:

$$\bar{w} = \frac{w}{L}, \quad \bar{x} = \frac{x}{L}, \quad \bar{P} = \frac{PL^2}{I_2}, \quad \bar{\mu} = \frac{\mu}{L}, \quad \bar{l} = \frac{l}{L} \quad (15)$$

The non-dimensional governing equation expression can be obtained as

$$\begin{aligned} \bar{P} \left(\frac{d^2 \bar{w}}{d\bar{x}^2} - \bar{\mu} \frac{d^4 \bar{w}}{d\bar{x}^4} \right) = & -\frac{d^2 X_1}{d\bar{x}^2} \frac{d^2 \bar{W}}{d\bar{x}^2} - 2 \frac{dX_1}{d\bar{x}} \frac{d^3 \bar{W}}{d\bar{x}^3} + \left(\bar{l}^2 \frac{d^2 X_1}{d\bar{x}^2} - X_1 \right) \frac{d^4 \bar{W}}{d\bar{x}^4} \\ & + 2\bar{l}^2 \frac{dX_1}{d\bar{x}} \frac{d^5 \bar{W}}{d\bar{x}^5} + \bar{l}^2 X_1 \frac{d^6 \bar{W}}{d\bar{x}^6} \end{aligned} \quad (16)$$

Solving the obtained governing equation gives the critical buckling load (\bar{P}) of the TDFGM Euler-Bernoulli nano-beams based on nonlocal strain gradient elasticity theory using generalized differential quadrature method (GDQM).

3. Results and discussion

It is proposed that the modulus of elasticity and density of the nano-beam vary in the x , y and z directions, as follows [87]

$$E(x, y, z) = e^{\frac{n_1}{L} x} \left[\left(\frac{2y+b}{2b} \right)^{n_2} + k \left(1 - \left(\frac{2y+b}{2b} \right)^{n_2} \right) \right] \left[E_c \left(\frac{2z+h}{2h} \right)^{n_3} + E_m \left(1 - \left(\frac{2z+h}{2h} \right)^{n_3} \right) \right] \quad (17)$$

$$\rho(x, y, z) = e^{\frac{n_4}{L}x} \left[\left(\frac{2y+b}{2b} \right)^{n_5} + k \left(1 - \left(\frac{2y+b}{2b} \right)^{n_5} \right) \right] \left[E_c \left(\frac{2z+h}{2h} \right)^{n_6} + E_m \left(1 - \left(\frac{2z+h}{2h} \right)^{n_6} \right) \right] \quad (18)$$

where, k , n_1 , n_2 , n_3 , n_4 , n_5 and n_6 are constant material parameters.

To verify the results, the results of this paper are compared with the results of previous work. To compare the results, strain gradient material length scale parameter and constant material parameters are considered zero. A comparison of the results is given in Table 1. Comparison of the results showed that the results of this study have acceptable accuracy.

Table 1. Comparison of the results of this work with other works.

$\bar{\mu}$	Ref.	
0	Present work	39.4783
	(Ghannadpour et al., 2013)	39.4784
	(Wang et al., 2006)	39.4786
	(Pradhan & Phadikar, 2009)	39.4784
	(Nejad et al., 2016)	39.4784
0.2	Present work	15.3068
	(Ghannadpour et al., 2013)	15.3068
	(Wang et al., 2006)	15.3068
	(Nejad et al., 2016)	15.3068
1	Present work	0.9753
	(Ghannadpour et al., 2013)	0.9753
	(Pradhan & Phadikar, 2009)	0.9753
	(Nejad et al., 2016)	0.9753

In Figure 1, the convergence of the buckling load calculated by the GDQ method is investigated. According to this figure, it can be concluded that with increasing nodes, the response converges. Considering 15 nodes ensures convergence.

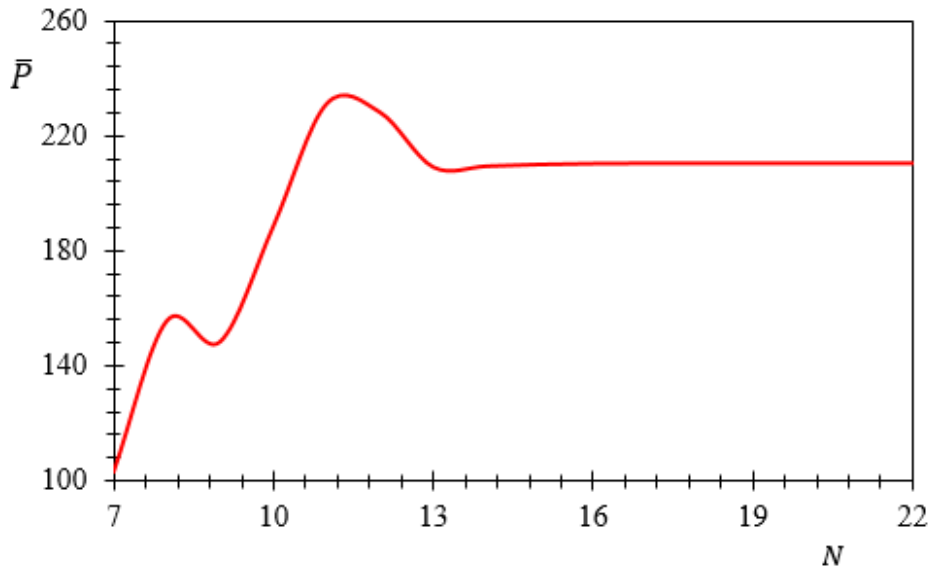


Fig. 1. The convergence of the buckling load calculated by the GDQ method for $\bar{\mu} = 2, \bar{l} = 2, n_1 = 2$

Figure 2 shows the changes in dimensionless buckling load in terms of nonlocal length scale parameter for different strain gradient length scale parameter. The results show that with increasing μ , the buckling load decreases, which shows that in the theory of nonlocal elasticity, the buckling load is lower than in the classical theory. In other words, the theory of non-local elasticity expresses the softening for a nanoscale material. In addition, with increasing strain gradient, the buckling load increases. This shows that by increasing the strain gradient length scale parameter, the material is more stable in nanoscale than in macro.

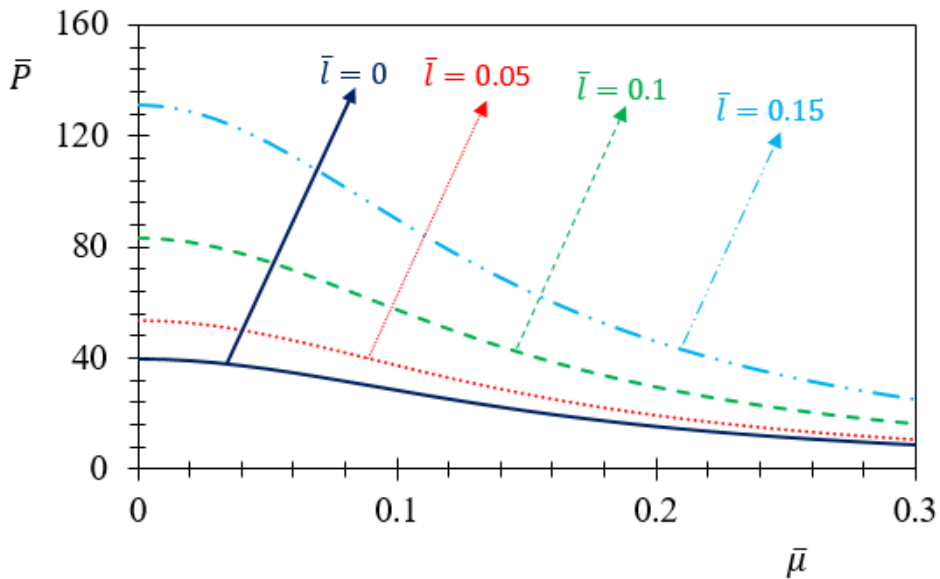


Fig. 2. changes in dimensionless buckling load in terms of nonlocal length scale parameter for different strain gradient length scale parameter and $n_1 = 0$

Dimensionless buckling load changes in terms of n_1 material parameter are shown in Figure 3. This figure shows that the buckling load increases with increasing n_1 . The reason for the increase in buckling load is the increase in modulus of elasticity with increasing n_1 .

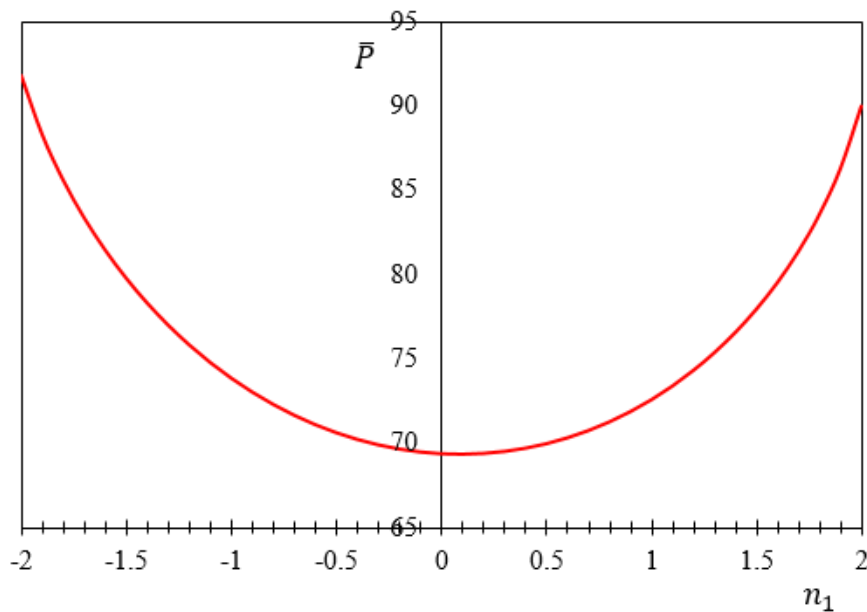


Fig. 3. Dimensionless buckling load changes in terms of n_1 material parameter for $\bar{\mu} = 0.2, \bar{l} = 0.2$

The buckling load changes in terms of n_2 material parameter for different buckling modes are shown in Figure 4. This figure shows that the buckling load for all modes decreases with increasing n_2 size. The reason for the decrease in buckling load is the decrease in modulus of elasticity with increasing n_2 .

Dimensional buckling load changes according to the material parameter n_3 for 4 buckling modes are shown in Figure 5. This figure shows that with increasing n_3 size, the buckling load increases for 4 buckling modes. The reason for increasing the buckling load is the increase in modulus of elasticity with increasing n_3 .

Figure 6 shows the buckling in terms of beam length for 3 states ($\bar{u} = 0 \bar{v} = 0$), ($\bar{u} = 1 \bar{v} = 2$) and ($\bar{u} = 2 \bar{v} = 1$). The results show that for the case that ($\bar{u} > \bar{v}$) softening is predicted for the material but for the case that ($\bar{u} < \bar{v}$) the hardening is predicted.

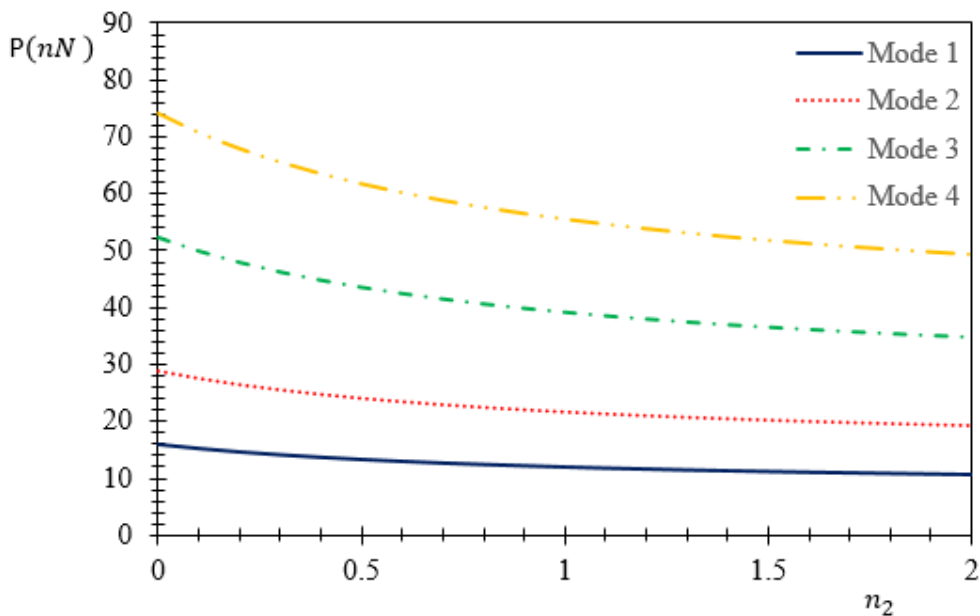


Fig. 4. The buckling load changes in terms of n_2 material parameter for different buckling modes for $\bar{\mu} = 0.2, \bar{l} = 0.2, n_1 = 0, n_3 = 0$

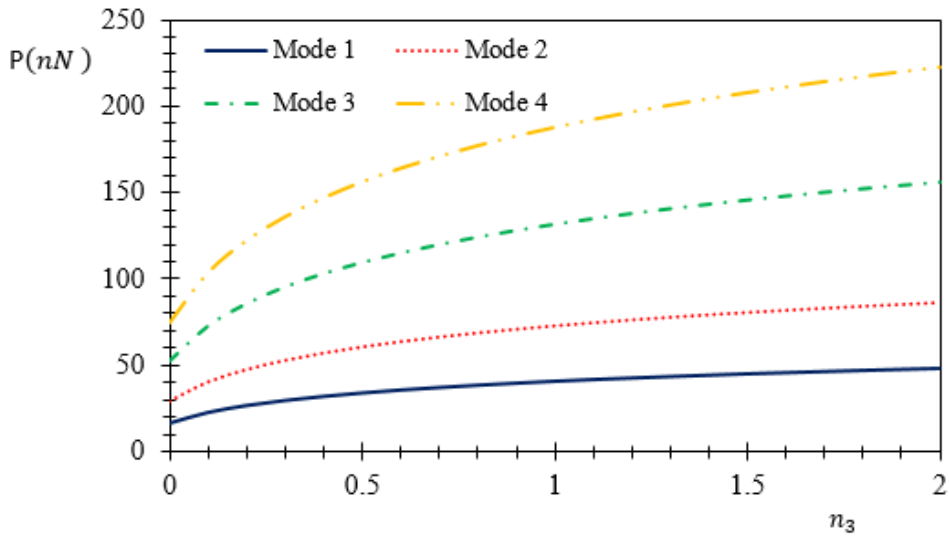


Fig 5. The buckling load changes in terms of n_3 material parameter for different buckling modes for $\bar{\mu} = 0.2, \bar{l} = 0.2, n_1 = 0, n_2 = 0$

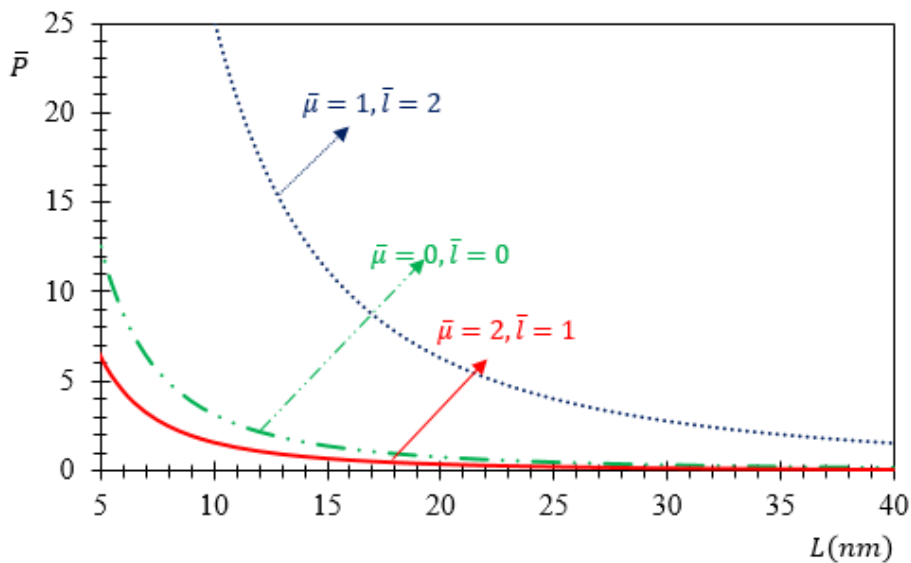


Fig. 6. The buckling load in terms of beam length for 3 states ($\bar{u} = 0 \bar{v} = 0$), ($\bar{u} = 1 \bar{v} = 2$) and ($\bar{u} = 2 \bar{v} = 1$)

4. Conclusion

In this paper, the effect of size for Bernoulli Euler nano beam made of three-dimensional functionally graded material is investigated using a combination of strain gradient theory and non-local elasticity. The results of this study showed that the strain gradient theory predicts hardening of the material at the nanoscale but the theory of non-local elasticity predicts the softening at the nanoscale. The combination of these two theories is able to predict both the hardening and softening effects at the nanoscale. In addition, the three-dimensional functionally graded

material in this paper has been investigated that the types of material changes in all directions of the beam have been considered with an arbitrary mathematical model. This model can be extended to a variety of nanostructures with different molecular structures.

References

- [1] A. Hadi, A. Rastgoo, N. Haghighipour, A. Bolhassani, Numerical modelling of a spheroid living cell membrane under hydrostatic pressure, *Journal of Statistical Mechanics: Theory and Experiment*, Vol. 2018, No. 8, pp. 083501, 2018.
- [2] M. Najafzadeh, M. M. Adeli, E. Zarezadeh, A. Hadi, Torsional vibration of the porous nanotube with an arbitrary cross-section based on couple stress theory under magnetic field, *Mechanics Based Design of Structures and Machines*, pp. 1-15, 2020.
- [3] A. Barati, A. Hadi, M. Z. Nejad, R. Noroozi, On vibration of bi-directional functionally graded nanobeams under magnetic field, *Mechanics Based Design of Structures and Machines*, pp. 1-18, 2020.
- [4] M. M. Khoram, M. Hosseini, A. Hadi, M. Shishehsaz, Bending analysis of bidirectional FGM Timoshenko nanobeam subjected to mechanical and magnetic forces and resting on Winkler–Pasternak foundation, *International Journal of Applied Mechanics*, Vol. 12, No. 08, pp. 2050093, 2020.
- [5] C. Kafadar, A. C. Eringen, Micropolar media—I the classical theory, *International Journal of Engineering Science*, Vol. 9, No. 3, pp. 271-305, 1971.
- [6] A. C. Eringen, Nonlocal polar elastic continua, *International journal of engineering science*, Vol. 10, No. 1, pp. 1-16, 1972.
- [7] A. C. Eringen, 2002, *Nonlocal continuum field theories*, Springer Science & Business Media,
- [8] A. C. Eringen, On differential equations of nonlocal elasticity and solutions of screw dislocation and surface waves, *Journal of applied physics*, Vol. 54, No. 9, pp. 4703-4710, 1983.
- [9] R. Mindlin, N. Eshel, On first strain-gradient theories in linear elasticity, *International Journal of Solids and Structures*, Vol. 4, No. 1, pp. 109-124, 1968.
- [10] R. A. Toupin, Elastic materials with couple-stresses, *Archive for Rational Mechanics and Analysis*, Vol. 11, No. 1, pp. 385-414, 1962.
- [11] C. Lim, G. Zhang, J. Reddy, A higher-order nonlocal elasticity and strain gradient theory and its applications in wave propagation, *Journal of the Mechanics and Physics of Solids*, Vol. 78, pp. 298-313, 2015.
- [12] A. Daneshmehr, A. Rajabpoor, A. Hadi, Size dependent free vibration analysis of nanoplates made of functionally graded materials based on nonlocal elasticity theory with high order theories, *International Journal of Engineering Science*, Vol. 95, pp. 23-35, 2015.
- [13] S. Pradhan, J. Phadikar, Bending, buckling and vibration analyses of nonhomogeneous nanotubes using GDQ and nonlocal elasticity theory, *Structural Engineering and Mechanics*, Vol. 33, No. 2, pp. 193-213, 2009.
- [14] J. Phadikar, S. Pradhan, Variational formulation and finite element analysis for nonlocal elastic nanobeams and nanoplates, *Computational materials science*, Vol. 49, No. 3, pp. 492-499, 2010.
- [15] J. K. Phadikar, S. C. Pradhan, Variational formulation and finite element analysis for nonlocal elastic nanobeams and nanoplates, *Computational Materials Science*, Vol. 49, No. 3, pp. 492-499, 9//, 2010.
- [16] M. Z. Nejad, A. Hadi, Non-local analysis of free vibration of bi-directional functionally graded Euler–Bernoulli nano-beams, *International Journal of Engineering Science*, Vol. 105, pp. 1-11, 2016/08/01/, 2016.
- [17] M. Z. Nejad, A. Hadi, Eringen's non-local elasticity theory for bending analysis of bi-directional functionally graded Euler–Bernoulli nano-beams, *International Journal of Engineering Science*, Vol. 106, pp. 1-9, 2016/09/01/, 2016.
- [18] M. Z. Nejad, A. Hadi, A. Rastgoo, Buckling analysis of arbitrary two-directional functionally graded Euler–Bernoulli nano-beams based on nonlocal elasticity theory, *International Journal of Engineering Science*, Vol. 103, pp. 1-10, 6//, 2016.
- [19] M. Hosseini, M. Shishesaz, K. N. Tahan, A. Hadi, Stress analysis of rotating nano-disks of variable thickness made of functionally graded materials, *International Journal of Engineering Science*, Vol. 109, pp. 29-53, 2016.

- [20] M. M. Adeli, A. Hadi, M. Hosseini, H. H. Gorgani, Torsional vibration of nano-cone based on nonlocal strain gradient elasticity theory, *The European Physical Journal Plus*, Vol. 132, No. 9, pp. 393, 2017.
- [21] M. Hosseini, H. H. Gorgani, M. Shishesaz, A. Hadi, Size-dependent stress analysis of single-wall carbon nanotube based on strain gradient theory, *International Journal of Applied Mechanics*, Vol. 9, No. 06, pp. 1750087, 2017.
- [22] M. Shishesaz, M. Hosseini, K. N. Tahan, A. Hadi, Analysis of functionally graded nanodisks under thermoelastic loading based on the strain gradient theory, *Acta Mechanica*, pp. 1-28, 2017.
- [23] F. Ebrahimi, M. R. Barati, A nonlocal higher-order refined magneto-electro-viscoelastic beam model for dynamic analysis of smart nanostructures, *International Journal of Engineering Science*, Vol. 107, pp. 183-196, 10//, 2016.
- [24] F. Ebrahimi, M. R. Barati, A. Dabbagh, A nonlocal strain gradient theory for wave propagation analysis in temperature-dependent inhomogeneous nanoplates, *International Journal of Engineering Science*, Vol. 107, pp. 169-182, 10//, 2016.
- [25] F. Ebrahimi, M. R. Barati, A nonlocal strain gradient refined beam model for buckling analysis of size-dependent shear-deformable curved FG nanobeams, *Composite Structures*, Vol. 159, pp. 174-182, 1/1/, 2017.
- [26] F. Ebrahimi, M. R. Barati, A. M. Zenkour, A new nonlocal elasticity theory with graded nonlocality for thermo-mechanical vibration of FG nanobeams via a nonlocal third-order shear deformation theory, *Mechanics of Advanced Materials and Structures*, No. just-accepted, 2017.
- [27] F. Ebrahimi, M. R. Barati, Vibration analysis of nonlocal beams made of functionally graded material in thermal environment, *The European Physical Journal Plus*, Vol. 131, No. 8, pp. 279, 2016.
- [28] F. Ebrahimi, M. R. Barati, Buckling analysis of nonlocal third-order shear deformable functionally graded piezoelectric nanobeams embedded in elastic medium, *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, pp. 1-16, 2016.
- [29] F. Ebrahimi, M. R. Barati, Magnetic field effects on buckling behavior of smart size-dependent graded nanoscale beams, *The European Physical Journal Plus*, Vol. 131, No. 7, pp. 1-14, 2016.
- [30] F. Ebrahimi, M. R. Barati, Magneto-electro-elastic buckling analysis of nonlocal curved nanobeams, *The European Physical Journal Plus*, Vol. 131, No. 9, pp. 346, 2016.
- [31] F. Ebrahimi, M. R. Barati, P. Haghi, Nonlocal thermo-elastic wave propagation in temperature-dependent embedded small-scaled nonhomogeneous beams, *The European Physical Journal Plus*, Vol. 131, No. 11, pp. 383, 2016.
- [32] F. Ebrahimi, M. Daman, Analytical investigation of the surface effects on nonlocal vibration behavior of nanosize curved beams, *ADVANCES IN NANO RESEARCH*, Vol. 5, No. 1, pp. 35-47, 2017.
- [33] F. Ebrahimi, A. Dabbagh, Nonlocal strain gradient based wave dispersion behavior of smart rotating magneto-electro-elastic nanoplates, *Materials Research Express*, Vol. 4, No. 2, pp. 025003, 2017.
- [34] L. Li, Y. Hu, Buckling analysis of size-dependent nonlinear beams based on a nonlocal strain gradient theory, *International Journal of Engineering Science*, Vol. 97, pp. 84-94, 12//, 2015.
- [35] A. Farajpour, M. Danesh, M. Mohammadi, Buckling analysis of variable thickness nanoplates using nonlocal continuum mechanics, *Physica E: Low-dimensional Systems and Nanostructures*, Vol. 44, No. 3, pp. 719-727, 2011.
- [36] L. Li, X. Li, Y. Hu, Free vibration analysis of nonlocal strain gradient beams made of functionally graded material, *International Journal of Engineering Science*, Vol. 102, pp. 77-92, 2016.
- [37] L. Li, Y. Hu, Wave propagation in fluid-conveying viscoelastic carbon nanotubes based on nonlocal strain gradient theory, *Computational Materials Science*, Vol. 112, Part A, pp. 282-288, 2/1/, 2016.
- [38] L. Li, Y. Hu, X. Li, Longitudinal vibration of size-dependent rods via nonlocal strain gradient theory, *International Journal of Mechanical Sciences*, Vol. 115-116, pp. 135-144, 9//, 2016.
- [39] L. Li, Y. Hu, Nonlinear bending and free vibration analyses of nonlocal strain gradient beams made of functionally graded material, *International Journal of Engineering Science*, Vol. 107, pp. 77-97, 10//, 2016.
- [40] L. Li, Y. Hu, Post-buckling analysis of functionally graded nanobeams incorporating nonlocal stress and microstructure-dependent strain gradient effects, *International Journal of Mechanical Sciences*, Vol. 120, pp. 159-170, 1//, 2017.
- [41] X. Li, L. Li, Y. Hu, Z. Ding, W. Deng, Bending, buckling and vibration of axially functionally graded beams based on nonlocal strain gradient theory, *Composite Structures*, Vol. 165, pp. 250-265, 4/1/, 2017.
- [42] G. Romano, R. Barretta, M. Diaco, F. M. de Sciarra, Constitutive boundary conditions and paradoxes in nonlocal elastic nanobeams, *International Journal of Mechanical Sciences*, Vol. 121, pp. 151-156, 2017.

- [43] G. Romano, R. Barretta, Stress-driven versus strain-driven nonlocal integral model for elastic nano-beams, *Composites Part B: Engineering*, Vol. 114, No. Supplement C, pp. 184-188, 2017/04/01/, 2017.
- [44] G. Romano, R. Barretta, Comment on the paper "Exact solution of Eringen's nonlocal integral model for bending of Euler-Bernoulli and Timoshenko beams" by Meral Tuna & Mesut Kirca, *International Journal of Engineering Science*, Vol. 109, No. Supplement C, pp. 240-242, 2016/12/01/, 2016.
- [45] J. Fernández-Sáez, R. Zaera, J. A. Loya, J. N. Reddy, Bending of Euler-Bernoulli beams using Eringen's integral formulation: A paradox resolved, *International Journal of Engineering Science*, Vol. 99, No. Supplement C, pp. 107-116, 2016/02/01/, 2016.
- [46] G. Romano, R. Barretta, Nonlocal elasticity in nanobeams: the stress-driven integral model, *International Journal of Engineering Science*, Vol. 115, No. Supplement C, pp. 14-27, 2017/06/01/, 2017.
- [47] A. Apuzzo, R. Barretta, R. Luciano, F. Marotti de Sciarra, R. Penna, Free vibrations of Bernoulli-Euler nano-beams by the stress-driven nonlocal integral model, *Composites Part B: Engineering*, Vol. 123, No. Supplement C, pp. 105-111, 2017/08/15/, 2017.
- [48] C. W. Lim, G. Zhang, J. N. Reddy, A higher-order nonlocal elasticity and strain gradient theory and its applications in wave propagation, *Journal of the Mechanics and Physics of Solids*, Vol. 78, No. Supplement C, pp. 298-313, 2015/05/01/, 2015.
- [49] L. Li, Y. Hu, Buckling analysis of size-dependent nonlinear beams based on a nonlocal strain gradient theory, *International Journal of Engineering Science*, Vol. 97, No. Supplement C, pp. 84-94, 2015/12/01/, 2015.
- [50] L. Li, Y. Hu, L. Ling, Flexural wave propagation in small-scaled functionally graded beams via a nonlocal strain gradient theory, *Composite Structures*, Vol. 133, No. Supplement C, pp. 1079-1092, 2015/12/01/, 2015.
- [51] A. Farajpour, M. H. Yazdi, A. Rastgoo, M. Mohammadi, A higher-order nonlocal strain gradient plate model for buckling of orthotropic nanoplates in thermal environment, *Acta Mechanica*, Vol. 227, No. 7, pp. 1849-1867, 2016.
- [52] F. Ebrahimi, M. R. Barati, A. Dabbagh, A nonlocal strain gradient theory for wave propagation analysis in temperature-dependent inhomogeneous nanoplates, *International Journal of Engineering Science*, Vol. 107, No. Supplement C, pp. 169-182, 2016/10/01/, 2016.
- [53] M. Tuna, M. Kirca, Exact solution of Eringen's nonlocal integral model for vibration and buckling of Euler-Bernoulli beam, *International Journal of Engineering Science*, Vol. 107, No. Supplement C, pp. 54-67, 2016/10/01/, 2016.
- [54] M. Tuna, M. Kirca, Exact solution of Eringen's nonlocal integral model for bending of Euler-Bernoulli and Timoshenko beams, *International Journal of Engineering Science*, Vol. 105, No. Supplement C, pp. 80-92, 2016/08/01/, 2016.
- [55] F. Ebrahimi, M. R. Barati, Dynamic Modeling of Magneto-electrically Actuated Compositionally Graded Nanosize Plates Lying on Elastic Foundation, *Arabian Journal for Science and Engineering*, Vol. 42, No. 5, pp. 1977-1997, May 01, 2017.
- [56] L. Li, X. Li, Y. Hu, Free vibration analysis of nonlocal strain gradient beams made of functionally graded material, *International Journal of Engineering Science*, Vol. 102, No. Supplement C, pp. 77-92, 2016/05/01/, 2016.
- [57] L. Li, Y. Hu, Nonlinear bending and free vibration analyses of nonlocal strain gradient beams made of functionally graded material, *International Journal of Engineering Science*, Vol. 107, No. Supplement C, pp. 77-97, 2016/10/01/, 2016.
- [58] J. Romanoff, J. N. Reddy, J. Jelovica, Using non-local Timoshenko beam theories for prediction of micro-and macro-structural responses, *Composite Structures*, Vol. 156, No. Supplement C, pp. 410-420, 2016/11/15/, 2016.
- [59] F. Ebrahimi, M. R. Barati, Vibration analysis of viscoelastic inhomogeneous nanobeams incorporating surface and thermal effects, *Applied Physics A*, Vol. 123, No. 1, pp. 5, December 10, 2016.
- [60] F. Ebrahimi, M. R. Barati, A nonlocal strain gradient refined beam model for buckling analysis of size-dependent shear-deformable curved FG nanobeams, *Composite Structures*, Vol. 159, No. Supplement C, pp. 174-182, 2017/01/01/, 2017.
- [61] X.-J. Xu, X.-C. Wang, M.-L. Zheng, Z. Ma, Bending and buckling of nonlocal strain gradient elastic beams, *Composite Structures*, Vol. 160, No. Supplement C, pp. 366-377, 2017/01/15/, 2017.

- [62] X. Li, L. Li, Y. Hu, Z. Ding, W. Deng, Bending, buckling and vibration of axially functionally graded beams based on nonlocal strain gradient theory, *Composite Structures*, Vol. 165, No. Supplement C, pp. 250-265, 2017/04/01/, 2017.
- [63] L. Li, Y. Hu, Torsional vibration of bi-directional functionally graded nanotubes based on nonlocal elasticity theory, *Composite Structures*, Vol. 172, No. Supplement C, pp. 242-250, 2017/07/15/, 2017.
- [64] M. Z. Nejad, P. Fatehi, Exact elasto-plastic analysis of rotating thick-walled cylindrical pressure vessels made of functionally graded materials, *International Journal of Engineering Science*, Vol. 86, pp. 26-43, 2015.
- [65] M. Z. Nejad, A. Rastgoo, A. Hadi, Exact elasto-plastic analysis of rotating disks made of functionally graded materials, *International Journal of Engineering Science*, Vol. 85, pp. 47-57, 2014.
- [66] Z. Mazarei, M. Nejad, A. Hadi, Thermo-elasto-plastic analysis of thick-walled spherical pressure vessels made of functionally graded materials, *International Journal of Applied Mechanics*, 2016.
- [67] M. Nejad, A. Rastgoo, A. Hadi, Effect of Exponentially-Varying Properties on Displacements and Stresses in Pressurized Functionally Graded Thick Spherical Shells with Using Iterative Technique, *Journal of Solid Mechanics Vol*, Vol. 6, No. 4, pp. 366-377, 2014.
- [68] M. Ghannad, G. H. Rahimi, M. Z. Nejad, Elastic analysis of pressurized thick cylindrical shells with variable thickness made of functionally graded materials, *Composites Part B: Engineering*, Vol. 45, No. 1, pp. 388-396, 2013.
- [69] M. Z. Nejad, M. Jabbari, M. Ghannad, Elastic analysis of FGM rotating thick truncated conical shells with axially-varying properties under non-uniform pressure loading, *Composite Structures*, Vol. 122, pp. 561-569, 2015.
- [70] M. Jabbari, M. Z. Nejad, M. Ghannad, Thermo-elastic analysis of axially functionally graded rotating thick cylindrical pressure vessels with variable thickness under mechanical loading, *International journal of engineering science*, Vol. 96, pp. 1-18, 2015.
- [71] M. Jabbari, M. Z. Nejad, M. Ghannad, Thermo-elastic analysis of axially functionally graded rotating thick truncated conical shells with varying thickness, *Composites Part B: Engineering*, Vol. 96, pp. 20-34, 2016.
- [72] M. Z. Nejad, G. Rahimi, M. Ghannad, Set of field equations for thick shell of revolution made of functionally graded materials in curvilinear coordinate system, *Mechanics*, Vol. 77, No. 3, pp. 18-26, 2016.
- [73] M. Ghannad, M. Z. Nejad, Elastic analysis of pressurized thick hollow cylindrical shells with clamped-clamped ends, *Mechanics*, Vol. 85, No. 5, pp. 11-18, 2016.
- [74] M. Z. Nejad, G. Rahimi, Deformations and stresses in rotating FGM pressurized thick hollow cylinder under thermal load, *Scientific Research and Essays*, Vol. 4, No. 3, pp. 131-140, 2009.
- [75] M. Z. Nejad, G. H. Rahimi, Elastic analysis of FGM rotating cylindrical pressure vessels, *Journal of the Chinese institute of engineers*, Vol. 33, No. 4, pp. 525-530, 2010.
- [76] P. Fatehi, M. Z. Nejad, Effects of material gradients on onset of yield in FGM rotating thick cylindrical shells, *International Journal of Applied Mechanics*, Vol. 6, No. 04, pp. 1450038, 2014.
- [77] C. Lü, C. W. Lim, W. Chen, Size-dependent elastic behavior of FGM ultra-thin films based on generalized refined theory, *International Journal of Solids and Structures*, Vol. 46, No. 5, pp. 1176-1185, 2009.
- [78] M. Lezgy-Nazargah, Fully coupled thermo-mechanical analysis of bi-directional FGM beams using NURBS isogeometric finite element approach, *Aerospace Science and Technology*, 2015.
- [79] M. Şimşek, Bi-directional functionally graded materials (BDFGMs) for free and forced vibration of Timoshenko beams with various boundary conditions, *Composite Structures*, Vol. 133, pp. 968-978, 2015.
- [80] S. Sahmani, M. M. Aghdam, Size dependency in axial postbuckling behavior of hybrid FGM exponential shear deformable nanoshells based on the nonlocal elasticity theory, *Composite Structures*, Vol. 166, pp. 104-113, 4/15/, 2017.
- [81] N. Tutuncu, Stresses in thick-walled FGM cylinders with exponentially-varying properties, *Engineering Structures*, Vol. 29, No. 9, pp. 2032-2035, 2007.
- [82] M. Z. Nejad, A. Hadi, A. Farajpour, Consistent couple-stress theory for free vibration analysis of Euler-Bernoulli nano-beams made of arbitrary bi-directional functionally graded materials, *Structural Engineering and Mechanics*, Vol. 63, No. 2, pp. 161-169, 2017.
- [83] A. Barati, M. M. Adeli, A. Hadi, Static torsion of bi-directional functionally graded microtube based on the couple stress theory under magnetic field, *International Journal of Applied Mechanics*, Vol. 12, No. 02, pp. 2050021, 2020.
- [84] M. A. Steinberg, Materials for aerospace, *Sci. Am.:(United States)*, Vol. 255, No. 4, 1986.

-
- [85] A. Hadi, M. Z. Nejad, M. Hosseini, Vibrations of three-dimensionally graded nanobeams, *International Journal of Engineering Science*, Vol. 128, pp. 12-23, 2018/07/01/, 2018.
- [86] M. R. Farajpour, A. Rastgoo, A. Farajpour, M. Mohammadi, Vibration of piezoelectric nanofilm-based electromechanical sensors via higher-order non-local strain gradient theory, *Micro & Nano Letters*, Vol. 11, No. 6, pp. 302-307, 2016.
- [87] A. Hadi, M. Z. Nejad, A. Rastgoo, M. Hosseini, Buckling analysis of FGM Euler-Bernoulli nano-beams with 3D-varying properties based on consistent couple-stress theory, *Steel and Composite Structures, An International Journal*, Vol. 26, No. 6, pp. 663-672, 2018.